

Direct Recycling of End-of-Life Lithium-Ion Batteries Cathode Active Materials by Hydrothermal Route

J. Castro^{1,2}, M. Gómez¹, P.J. Acebes¹, P. Moretti¹, M.R. Bermejo¹, M. Merlo³, Y. Belce³ and J.J. Biendicho³

¹CARTIF Technology Centre, Area of Circular Economy, Boecillo, Valladolid, 47151, Spain

²Institute of Sustainable Processes, University of Valladolid, Valladolid, 47011, Spain

³Catalonia Institute for Energy Research (IREC), Sant Adrià de Besòs, Barcelona, 08930, Spain

Keywords: Direct Recycling, Lithium-Ion Batteries, Hydrothermal re-lithiation

Presenting author email: juacas@cartif.es

In the search for new renewable energy solutions, Lithium-Ion Batteries (LIBs) are one of the most promising solutions in recent decades, offering high energy density, long life and multidisciplinary applications. Thanks to these advantages, LIBs have been perfectly integrated into energy storage, both for stationary use in homes and industry, and for powering the electric motors of heavy vehicles or light personal transport. The scientific community's intense research into the vagaries of lithium-ion chemistry has catalysed remarkable innovation and presented numerous paradigms to elucidate the fundamentals of LIB technologies in their ever-evolving permutations.

Inside LIBs there is an interplay of cathode and anode materials, electrolytes and separators. This ensemble allows lithium ions to move effectively and reversibly between the anode and cathode during charging and discharging. However, new electrode materials, electrolyte formulations and manufacturing processes have been required for the next generation of LIBs to improve performance and sustainability. As is continued to unravel the complex web of LIBs technology, researchers face a myriad of issues ranging from capacity degradation to safety and the environmental footprint of raw materials. In response, their efforts are increasingly focused on not only addressing these concerns, but also integrating sustainability across the entire battery lifecycle. From advanced recycling technologies that recover valuable materials from spent batteries to the search for environmentally friendly alternatives in manufacturing, these solutions underscore the scientific community's commitment to creating a sustainable and circular LIBs value chain, where advances in design, materials and recycling technology converge to deliver minimal environmental impact and maximum resource efficiency.

The end-of-life (EoL) management of LIBs is a critical mainstream consideration as a major secondary source of valuable materials such as cobalt, nickel, manganese, lithium and graphite, among others. Their recycling is currently a headache, solved by non-100% green technologies such as pyrometallurgy or inorganic acid leaching (hydrometallurgy), which do not reduce the battery footprint and produce secondary wastewater, respectively. However, achieve good recovery rates per critical raw material, depending on the type of LIB. Recently, there has been a move away from the conventional and destructive acid leaching process. Pyrometallurgy is a high-temperature melting process that includes thermal treatment and chemical separation. The hydrometallurgical process involves the solubilisation of target metallic elements from black mass of LIBs in a leaching solution and reclaiming the metals via the further stage of separation and purification. Direct recycling stands out as a method of regenerating degraded cathode material without compromising its original structure. This approach represents a significant advancement, with various techniques such as electrochemical relithiation (Yang, 2020; Zhang, 2020), solid-state synthesis (Nie, 2015; Gao, 2020), and hydrothermal relithiation (Xu, 2021; Sloop, 2019) gaining prominence for their enhanced sustainability and reduced environmental impact. Thus, direct recycling is becoming more attractive to researchers and recycling stakeholders due to its high recovery rate and improved sustainability, but large-scale developments are not yet underway.

The battery recycling market is growing rapidly due to the need for critical raw materials and new European policies to reduce material dependency from other countries outside the European Union, however, currently the amount of industrial battery recycling facilities is not enough established to cover the significant volumes of first generation EoL LIBs from electric vehicles for the next decade. Considering that global battery demand is expected to grow by 25% per year to reach 2,600 GWh in 2030 (Fleischmann, 2023), the need for efficient industrial recycling solutions are critical. With this in mind, research projects worldwide are exploring cutting-edge technologies to enhance recycling rates and diminish the environmental impact of the battery industry.

Direct recycling process is divided in two well-defined steps such as fine disassembly and separation, and the relithiation step. This study aimed to directly recycle NMC-622 cathode active material (CAM) from the EoL LIB of an electric vehicle (EV), through prior efficient cell disassembly and the use of high intensity ultrasonic pre-processing to detach the CAM from the aluminium current collectors of the cathodes of LGX E63B pouch

cells. This NMC chemistry of LIBs currently dominates the market and is a typical layered Li transition metal oxide cathode material. Long-term use (charge-discharge) can lead to various component and structural failures such as loss of active lithium, dissolution of transition metal ions, mixing of nickel and lithium, or dendrite formation over the anode, among others, which significantly degrade the performance of the NMC cathode material (Kang, 2021; Jiang, 2021; Yin, 2021).

Fine disassembly and separation step were achieved after the deactivation process. Before the manipulation of the pouch cells, deep discharging was achieved to reduce electrical risks during cell disassembly, followed by a second safety measure of freezing to -18°C for 24h prior to manual cell opening, which was performed in a fume hood to separate casing, anode, cathode and separator. A vacuum oven was then used to evaporate and condense the electrolyte. Free-electrolyte cathode electrodes were passed through a high-intensity ultrasonication step to reach CAM. Owing to the strong adhesive properties of the polyvinylidene fluoride (PVDF) binder, the CAM was detached from the aluminium current collector in a solvent solution at room temperature. Several solvents were tested to achieve the highest separation efficiency ($>96\%$) of the ultrasonication pre-processing. The detached CAM was then filtered, dried at 90°C for 24 h and then ground into a fine powder for subsequent hydrothermal route. Later, the re-lithiation step was carried out in a hydrothermal reactor at 220°C during 2h by adding several Lithium salts to modify the chemical composition of the cathode powder, such as Lithium Hydroxide and Lithium Sulphate. Afterwards sintering at 850°C during 4h was carried out in a muffle to reach the healed CAM for the electrochemical performance. To check the viability of the recycling process, the CAM was tested in half-cell using a Celgard 2400 separator and LiPF_6 DEC: EC electrolyte in the voltage range 2.7 - 4.2 V vs Li metal. Figure 1 shows how this direct recycling route fits inside the LIBs value chain.

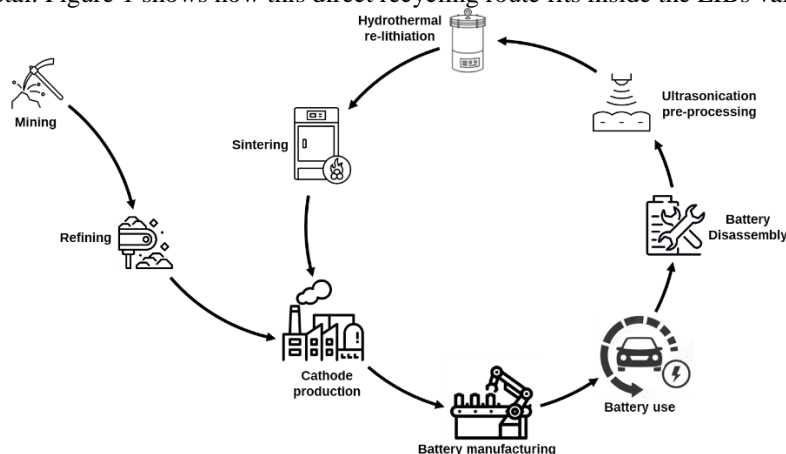


Figure 1. Integration of direct recycling through hydrothermal route inside battery value chain.

The regenerated NMC-622 cathode material demonstrates a discharge capacity of 150 mAh/g at 0.05C during activation and 100 mAh/g at 0.1C with a capacity retention of 80% after 100 cycles. These electrochemical results align with state-of-the-art NMC622 cathode materials that are commercially available. The recycling approach outlined in this study is not only straightforward but also scalable, offering a potential avenue to tackle the environmental issues associated with large quantities of end-of-life lithium-ion batteries (EoL LIBs).

Fleischmann, J., Hanicke, M., Horetsky, E., Ibrahim, D., Jautelat, S., Linder, M., Schaufuss, P., Torscht, L., & van de Rijt, A. (2023). Battery 2030: Resilient, sustainable, and circular. McKinsey & Company, 2-18.

Yang, T., Lu, Y., Li, L., Ge, D., Yang, H., Leng, W., Zhou, H., Han, X., Schmidt, N., Ellis, M. & Li, Z. (2020). An effective relithiation process for recycling lithium-ion battery cathode materials. *Advanced Sustainable Systems*, 4(1), 1900088.

Zhang, L., Xu, Z., & He, Z. (2020). Electrochemical relithiation for direct regeneration of LiCoO_2 materials from spent lithium-ion battery electrodes. *ACS Sustainable Chemistry & Engineering*, 8(31), 11596-11605.

Nie, H., Xu, L., Song, D., Song, J., Shi, X., Wang, X., Zhang, L. & Yuan, Z. (2015). LiCoO_2 : recycling from spent batteries and regeneration with solid state synthesis. *Green chemistry*, 17(2), 1276-1280.

Gao, H., Yan, Q., Xu, P., Liu, H., Li, M., Liu, P., Luo, J. & Chen, Z. (2020). Efficient direct recycling of degraded LiMn_2O_4 cathodes by one-step hydrothermal relithiation. *ACS applied materials & interfaces*, 12(46), 51546-51554.

Xu, P., Yang, Z., Yu, X., Holoubek, J., Gao, H., Li, M., Cai, G., Bloom, I., Liu, H., Chen, Y., An, K., Papek, K. Z., Liu, P. & Chen, Z. (2021). Design and optimization of the direct recycling of spent Li-ion battery cathode materials. *ACS Sustainable Chemistry & Engineering*, 9(12), 4543-4553.

Sloop, S. E., Crandon, L., Allen, M., Lerner, M. M., Zhang, H., Sirisaksoontorn, W., Gaines, L., Kim, J. & Lee, M. (2019). Cathode healing methods for recycling of lithium-ion batteries. *Sustainable Materials and Technologies*, 22, e00113.

Kang, Y. S., Park, S. Y., Ito, K., Kubo, Y., Shin, Y., Kim, D. Y., Seo, D., Kim, S., Park, J., Doo, S., Koh, M., Seo, J. A. & Park, K. (2021). Revealing the structural degradation mechanism of the Ni-rich cathode surface: How thick is the surface?. *Journal of power sources*, 490, 229542.

Jiang, M., Danilov, D. L., Eichel, R. A., & Notten, P. H. (2021). A review of degradation mechanisms and recent achievements for Ni-rich cathode-based Li-ion batteries. *Advanced Energy Materials*, 11(48), 2103005.

Yin, S., Deng, W., Chen, J., Gao, X., Zou, G., Hou, H., & Ji, X. (2021). Fundamental and solutions of microcrack in Ni-rich layered oxide cathode materials of lithium-ion batteries. *Nano Energy*, 83, 105854.